



POLISH ACADEMY OF SCIENCES - COMMITTEE OF MATERIALS SCIENCE
SILESIA N UNIVERSITY OF TECHNOLOGY OF GLIWICE
INSTITUTE OF ENGINEERING MATERIALS AND BIOMATERIALS
ASSOCIATION OF ALUMNI OF SILESIA N UNIVERSITY OF TECHNOLOGY

Conference
Proceedings

12th INTERNATIONAL SCIENTIFIC CONFERENCE
ACHIEVEMENTS IN MECHANICAL & MATERIALS ENGINEERING

Employment of a high power diode laser for alloying the X40CrMoV5-1 steel surface layer with tungsten carbide[#]

L.A. Dobrzański ^{a,*}, M. Bonek ^{a,*}, E. Hajduczek ^{a,*}, A. Klimpel ^b

^aInstitute of Engineering Materials and Biomaterials, Faculty of Mechanical Engineering, Silesian University of Technology, ul. Konarskiego 18a, 44-100 Gliwice, Poland

^bDepartment of Welding, Faculty of Mechanical Engineering, Silesian University of Technology, ul. Konarskiego 18a, 44-100 Gliwice, Poland

The paper presents the effect of alloying with tungsten carbide on properties of the X40CrMoV5-1 steel surface layer, using the high power diode laser (HPDL). Selection of laser operating conditions is discussed, as well as thickness of the alloying layer, and their influence on structure and chemical composition of the steel. Analysis of the process conditions influence on thicknesses of the alloyed layer and heat-affected zone is presented.

1. INTRODUCTION

Improvement of surface properties of materials used to date features one of the goals set to the research institutions active in the materials engineering area. Possibilities of increasing the functional properties of the hot-work alloy tool steels by modification of their chemical composition in a conventional way are very limited already. Laser technique features the especially promising tool for solving the contemporary surface engineering problems thanks to the physical properties of the laser beam, making it possible to focus precisely the delivered energy in the form of heat in the surface layer. Moreover, methods which are not based on partial melting of surface alone, but on partial melting with the simultaneous introduction of the alloying elements with high hardness, like carbides, are being employed more and more widely for modification of the surface layer. High cooling rates are obtained in this process and its end result is the fine-grained material with the super-cooled phases. Material transport in the liquid metal, caused by the surface tension forces, features the main factor deciding development of the alloyed layers. The non-uniform material heating resulting from the laser beam impact causes development of a big surface tension gradient on the surface of the liquid. The force is directed outside from the beam centre where is the highest temperature value to its edge and causes movement of the molten material. The convection circulation in the molten material pool is shown schematically in Figure 1.

* Authors participate in the CEEPUS No PL-013/03-04 project headed by Prof. L.A. Dobrzański.

[#] Investigations were financed within the framework of the Polish State Committee for Scientific Research No 4 T08C 051 25 grant headed by Dr. E. Hajduczek.

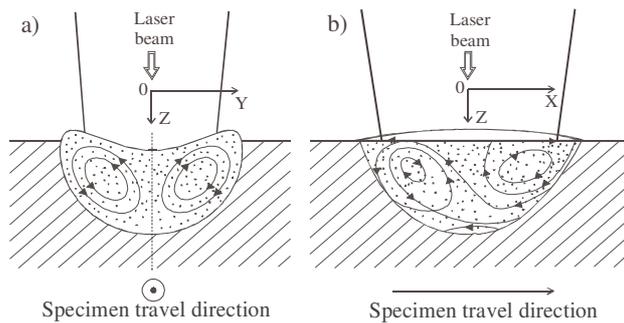


Fig. 1. Convection circulation schema in the pool developed by laser impact on the steel surface; a) perpendicularly to the specimen travel direction, b) in parallel to the specimen travel direction

Density of power delivered to the surface layer of the processed materials is lower for the more and more often used HPDL type lasers compared to its single mode distribution characteristic for other laser types; however, the energy is distributed more uniformly across the rectangular area of the laser beam focus. Therefore, the HPDL laser is ideally suited for modification of the surface layer of materials. Moreover, employment of the appropriate shielding gases and correctly selected nozzle shape, and its position in respect to the processed material, have the objective to ensure the high quality of weld face and repeatability of the obtained

results. The advantages of laser treatment compared to other surface layer modification methods are: high processing rate, possibility to carry out treatment without protective guards, modification of small, arbitrarily selected fragments of the processed surfaces responsible for tools and machine elements life, as well as its material economy.

The goals of this work were: determining the technological conditions for alloying with the tungsten carbide the hot-work alloy steel surface layer using the high power diode laser (HPDL) and determining the relationship between the laser treatment parameters and structure and chemical composition of the steel.

2. EXPERIMENTAL PROCEDURE

The material under investigation were specimens from the X40CrMoV5-1 hot-work alloy tool steel, obtained from the vacuum cast, delivered in the form of bars with O.D. 75 mm. Specimens of O.D. 70 mm and 6 mm thick were turned from the material delivered in a softened state, further they were austenitized in a salt bath furnace and tempered in the chamber furnace with argon protective atmosphere. The specimens were heated gradually to the austenitizing temperature with holding at 650°C for 15 min and were austenitized for 30 min at the temperature of 1060°C. Cooling was carried out in the hot oil. The specimens were tempered twice after quenching, each time for 2 hours, at the temperature of 510°C.

The specimens' surfaces were sand blasted and ground on a surface grinder with the magnetic holder. The paste containing the WC tungsten carbide powder with the inorganic binder was applied on the degreased specimens as 0.06 mm and 0.11 mm thick layers. The specimens from the X40CrMoV5-1 steel, mounted on a turntable, were penetrated with the Rofin DL 020 high power diode laser (HPDL) beam. Two fusion tracks were made on each specimen face with radii of 12 mm and 22 mm. Dimensions of the laser beam focused on the material surface are 1.8 x 6.8 mm. The working focal distance (measured from the head protective glass) is 92 mm. Fusion was carried out in the direction perpendicular to the longer side of the focused beam with the multi-mode energy distribution, which ensures obtaining the wide weld face.

Metallographic examinations of the material structures after laser alloying its surface layer were made on LEICA MEF4A light microscope with magnifications from 100 to 1000x. Structure examinations and thickness measurement of the relevant zones in the surface layer were made also on the transverse micro-sections on the OPTON DSM 940 scanning electron microscope with magnifications from 1000 to 5000x. Examinations of the chemical composition in micro-zones and analyses of the linear distribution of alloying elements in specimens from the investigated steel were made on the OPTON DSM-940 scanning electron microscope with the Oxford EDS LINK ISIS energy dispersive X-ray spectrometer with the 20 kV accelerating voltage.

3. ANALYSIS OF EXPERIMENTAL RESULTS

In case of alloying with the tungsten carbide powder, whose melting point is much higher than the melting point of steel, with the initially specified laser power, inundation occurs of the un-molten WC powder grains into the molten steel substrate. Strong circulation of the liquid metal was discovered with rapid solidification after the laser beam has passed, leading to freezing of the structure. It was found out, basing on metallographic examinations, that the structure of the material solidifying after laser fusion is characterized by occurrences of areas with the diversified morphology (Fig. 2a) connected with crystallization of the steel. Depending on the processing parameters used various material mixing mechanisms were observed. At low laser material penetration energy values the capillary lines are not connected and the fusion structure is relatively homogeneous. Along with the laser power growth the occurrences of capillary lines' swirls were observed. Big dendrites occur in the boundary zone between the solid and liquid phases, whose main axes are oriented according to the heat abstraction directions. Repeated crystal growth direction changes are observed, characteristic

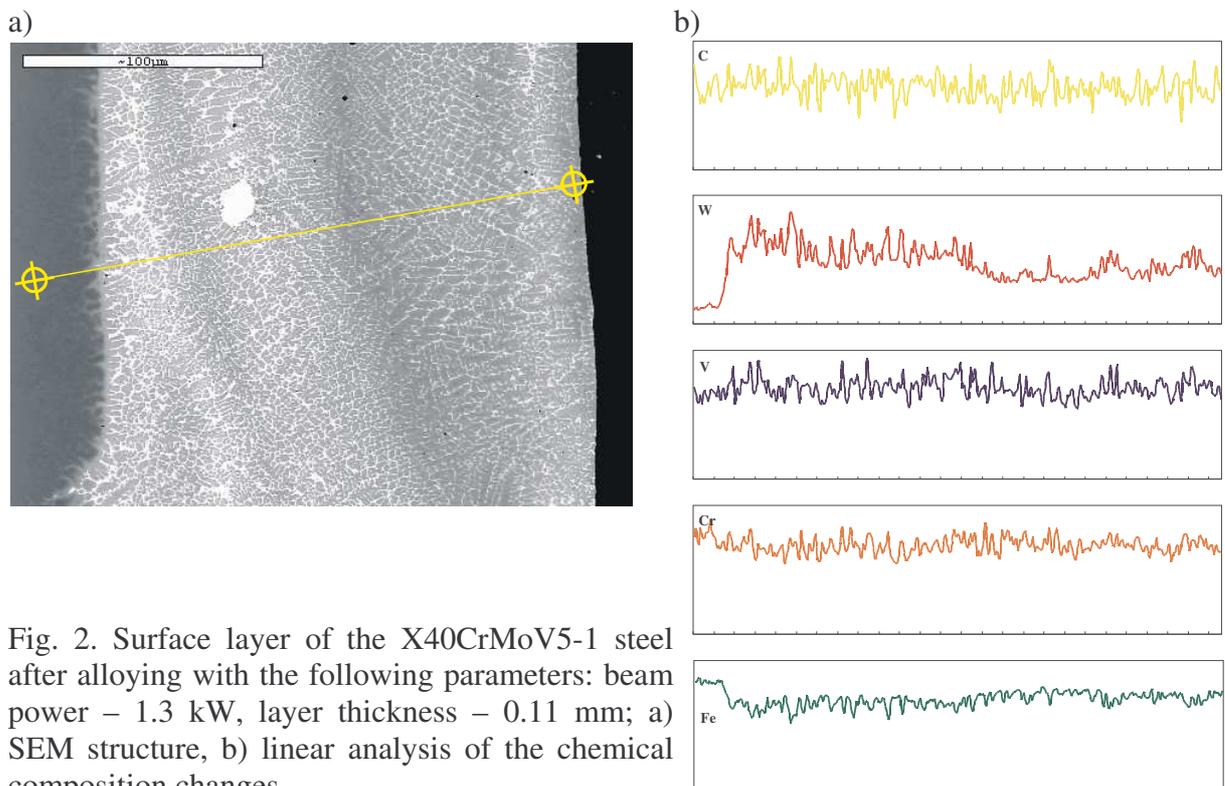


Fig. 2. Surface layer of the X40CrMoV5-1 steel after alloying with the following parameters: beam power – 1.3 kW, layer thickness – 0.11 mm; a) SEM structure, b) linear analysis of the chemical composition changes

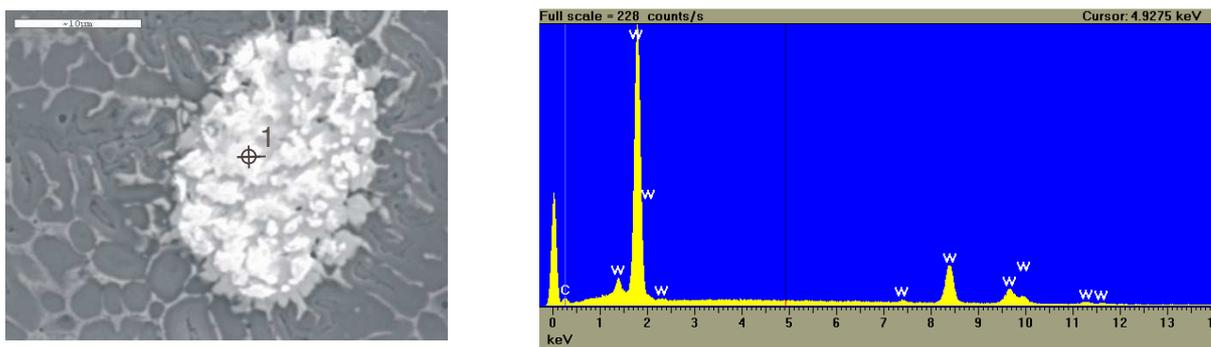


Fig. 3. Microstructure of the X40CrMoV5-1 steel (SEM) after alloying with the following parameters: beam power – 0.9 kW, layer thickness – 0.11 mm and the plot of intensity versus energy dispersive X-ray radiation, representing the pointwise WC carbide chemical composition analysis

for these zones. Structure of fine equiaxed crystals with the carbide lattice develops in the central zone of the fused area where heat abstraction takes place in all directions. Linear analysis of the chemical composition revealed tungsten presence in the fused zone only (Fig. 2b). No tungsten presence was found in the heat affected zone. Undissolved tungsten carbides were revealed surrounded by the dense lattices of the superfine eutectic mixture (Fig. 3).

It was found out that laser fusion results in refinement of structure in the entire laser power range. Different grain size was revealed during examinations in the particular zones of the surface layer after laser alloying. Matrix grains shape and size does not change during fusion. Only at the crystallization front, between the fused and heat affected zones, the elongated and smaller grains were found, which are subjected to partial melting and re-crystallization during laser modification.

4. SUMMARY

Alloying the investigated steel with tungsten carbide causes development of the surface layer, in which one can point out the fused zone, heat affected zone, and interface zones. Their thickness is closely connected with the fusion parameters, and thickness of the fused layer changes significantly along with the laser beam power increase. A fine-grained, dendritic structure was obtained in the fused zone, with the crystallographic orientation connected with the dynamical heat abstraction from the laser beam impact zone. Occurrences of the un-fused tungsten carbide grains were observed in the structure and the increased tungsten content compared to the native material, whose variable concentration is connected with the molten metal fluctuation in the pool during alloying.

BIBLIOGRAPHY

1. L.A. Dobrzański, M. Bonek, E. Hajduczek, A. Klimpel, A. Lisiecki: Application of high power diode laser (HPDL) for alloying of X40CrMoV5-1 steel surface layer by tungsten carbides. International Conference on Advanced Materials & Processing Technologies, AMPT 2003, Dublin, 2003, 77-80;
2. L.A. Dobrzański, M. Bonek, A. Klimpel, A. Lisiecki: Surface layer's structure of X40CrMoV5-1 steel remelted and/or WC alloyed with HPDL laser, Materials Science Forum, Vols. 437-438, 2003, 69-72.